

UN38.3 检测报告 UN38.3 Test Report

产品名称: 圆柱锂离子电芯 INR18650K 2200mAh

Name of Products: Cylindrical Lithium Ion Cell INR18650K 2200mAh

委托单位: 深圳市东恒新能源科技有限公司

Client: Shenzhen Dongheng New Energy Technology Co., LTD

制造商: 深圳市东恒新能源科技有限公司

Manufacturer: Shenzhen Dongheng New Energy Technology Co., LTD

签发日期:

2018-01-02

Date of issue:

深圳市北测检测技术有限公司 Shenzhen NTEK Testing Technology Co., Ltd.





Manufacturer	Shenzhen Dongheng New Energy Technology Co., LTD
制造商	深圳市东恒新能源科技有限公司
Address of manufacturer	Zhuqing Road No.1, Caopu Village, Shijing Community, Pingshan
制造商地址	Office, Pingshan New District, Shenzhen City, Guangdong Province,
	China
	广东省深圳市坪山新区坪山办事处石井社区草埔村竹青路 1号
Factory	Shenzhen Dongheng New Energy Technology Co., LTD
エ厂	深圳市东恒新能源科技有限公司
Address of factory	Zhuqing Road No.1, Caopu Village, Shijing Community, Pingshan
工厂地址	Office, Pingshan New District, Shenzhen City, Guangdong Province,
	China
	广东省深圳市坪山新区坪山办事处石井社区草埔村竹青路 1号
Name of Products	Cylindrical Lithium Ion Cell
产品名称	圆柱锂离子电芯
Model/type reference	INR18650K 2200mAh
型号	INIC 10030IC 2200IIIAII
Trade Mark	
商标	

Tested according to 测试依据:

Recommendations on the TRANSPORT OF DANGEROUS GOODS, Manual of Test and Criteria, PART III, section 38.3 Lithium metal and lithium ion batteries, the sixth revised edition (ST/SG/AC.10/11/Rev.6). 联合国《关于危险货物运输的建议书,试验和标准手册》,第三部分,38.3节锂金属和锂离子电池要求,第 六修订版 (ST/SG/AC.10/11/Rev.6)

Tests performed 测试项目:

Test T.1: Altitude simulation 试验 T.1: 高度模拟

Test T.5: External short circuit 试验 T.5: 外部短路 Test T.6: Impact 试验 T.6: 撞击

Test T.2: Thermal Test 试验 T.2: 温度试验

Test T.8: Forced discharge 试验 T.8: 强制放电 Test T.3: Vibration 试验 T.3: 振动

Test T.4: Shock 试验 T.4: 冲击

Test Conclusion 试验结论:

The Cylindrical Lithium Ion Cell submitted by Shenzhen Dongheng New Energy Technology Co., LTD is tested according to the Recommendations on the TRANSPORT OF DANGEROUS GOODS, Manual of Test and Criteria. PART III. section 38.3 Lithium metal and lithium ion batteries, the sixth revised edition (ST/SG/AC.10/11/Rev.6).

Test results: PASS

由深圳市东恒新能源科技有限公司提交的圆柱锂离子电芯按照联合国《关于危险货物运输的建议书,试 验和标准手册》,第三部分,38.3 节锂金属和锂离子电池要求,第六修订版 (ST/SG/AC.10/11/Rev.6)进行测

测试结果: 合格

Tested by: 主检人:

Reviewed by:

审核人:

Approved by


批准人:

Seal of NIEK

报告单位(盖章

Page 2 of 14 第2页 共14页

Shenzhen NTEK Testing Technology Co., Ltd. Fax: +86-755-6115 6599 Tel: +86-755-6115 6588 http://www.ntek.org.cn





General product information	ation 通用产品信息:		
Nominal Voltage 标称电压	3.7V	Rated Capacity 额定容量	2200mAh (8.14Wh)
Standard Charging Current 标准充电电流	1100mA	Max. Continuous Charging Current 最大充电电流	4400mA
Limited Charging Voltage 充电限制电压	4.2V	Cut-Off Voltage 放电截止电压	2.75V
Standard Continuous Discharge Current 标准放电电流	1100mA	Max. Continuous Discharge Current 最大放电电流	4400mA
Appearance 外观	Pink and Cylindrical 圆柱形、粉红色	Classification 类别	Small Lithium ion Cells 小型锂离子电芯
Size (D×H) 尺寸	18.4×65.0mm		

Date of receipt of test item	2016-07-13	Completion Date	2017-03-03
接收日期	13166	完成日期	

Remarks 备注说明:

Cells of A1#-A10# are fully charged at first cycle;

Cells of A11#-A15# at 50% of the design rated capacity at first cycle;

Cells of A16#-A25# are fully discharged at first cycle;

Cells of A26#-A35# are fully discharged after 50 cycles;

Test environment condition: Room temperature: 15-25°C, Room humidity: 40-70%

Note: All test data of this report are based on the original test report NTEK-2017DC0218007S, dated by 2017-03-03.

电芯 A1#-A10#为首次循环满电状态;

电芯 A11#-A15#为首次循环 50%充电状态;

电芯 A16#-A25#为首次循环完全放电状态;

电芯 A26#-A35#为 50 个循环后完全放电状态;

试验环境条件:环境温度: 15-25°C,环境湿度: 40-70%

注:本报告中的所有测试数据基于原始报告 NTEK-2017DC0218007S, 出版日期为 2017-03-03。

Summaries of testing 测试摘要:

Each cell type is subjected to tests T.1 to T.8. Tests T.1 to T.5 are conducted in sequence on the same cells. Tests 6 and 8 are conducted using not otherwise tested cells.

每一种类型的电芯均应进行T.1至T.8项试验。电芯必须按顺序在相同的一组电芯上进行试验T.1至T.5。试验T.6和T.8应使用未另外试验过的电芯。

In order to quantify the mass loss, the following procedure is provided:

Mass loss(%)= $(M_1-M_2)/M_1 \times 100$





为了量化质量损失,可用以下公式计算:

质量损失(%)=(M₁-M₂)/M₁×100

Where M_1 is the mass before the test and M_2 is the mass after the test. When mass loss does not exceed the values in Table below, it is considered as "no mass loss".

式中: M_1 是试验前的质量, M_2 是试验后的质量。如果质量损失不超过下表所列的数值, 应视为"无质量损失"。

Mass M of cell or battery	Mass loss limit
电芯或电池的质量	质量损失限值
M<1g	0.5%
1g≤M≤75g	0.2%
M>75g	0.1%

In tests T.1 to T.4, cells meet this requirement if there is no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell after testing is not less than 90% of its voltage immediately prior to this procedure.

在T.1至T.4的试验中,电芯须满足无渗漏、无泄气、无解体、无破裂和无起火,并且每个试验电芯在试验后的开路电压不小于其在进行这一试验前电压的90%。

Test equipments 检测设备:

N170 Battery test system 电池检测系统

N171 Electronic balance 电子天平

N172 Low pressure chamber 低气压试验箱

BAT-0017 Programmable Temperature & Humidity Controller 可程式恒温恒湿箱

N173 Vibration test system 振动测试系统

N174 Hydraulic Hoist Vertical Shock System 液压垂直冲击系统

N175 Short circuit tester 短路测试机

N177 Explosion-proof chamber 防爆箱

N178 DC Source 直流电源


N180 Digital multimeter 数字式万用表

N185 uR1000 recorder uR1000 记录仪

N176 Battery Impact tester 电池撞击试验机





Test Procedure 测试程序

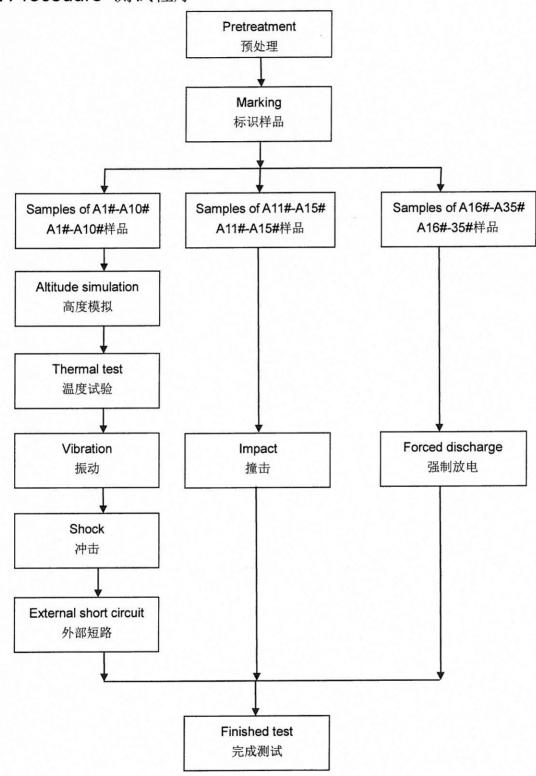




Photos of sample 样品照片

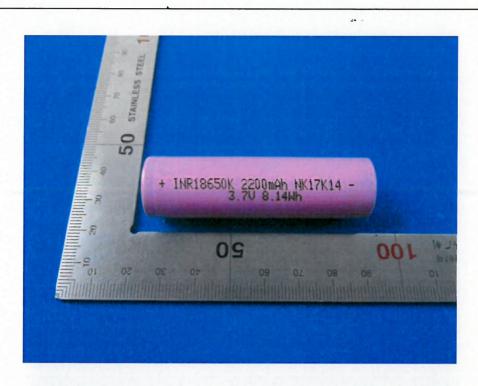

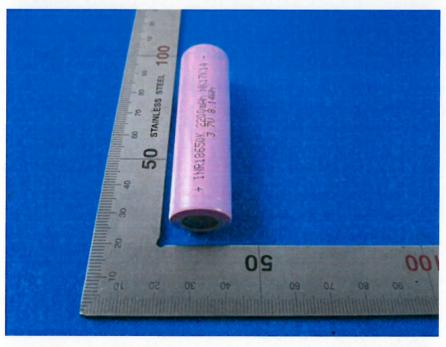





Test results 测试结果:

Test T.1: Altitude simulation 试验T.1: 高度模拟

Test method 测试方法

Cells are stored at a pressure of 11.6 kPa or less for at least six hours at ambient temperature (20 \pm 5 °C). 试验电芯被放置在压力等于或低于11.6 kPa和环境温度(20±5°C)下存放至少6小时。

Requirement 要求

Cells meet this requirement if there is no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell after testing is not less than 90% of its voltage immediately prior to this procedure.

电芯须无渗漏、无泄气、无解体、无破裂和无起火,并且每个试验电池在试验后的开路电压不小于其在进行这一 试验前电压的90%。

Test Data showed in table below 测试数据见下表

		Prior to te	est 试验前	After tes	t 试验后		Voltage after	
State of samples 样品状态	No. 编号	Mass 质量 (g)	Voltage 电压 (V)	Mass 质量 (g)	Voltage 电压 (V)	Mass loss 质量损 失 (%)	test/ voltage prior to test (%) 试验后电压/ 试验前电压	Results 结果
	A1#	43.548	4.17	43.548	4.17	0.00	100.0	PASS 合格
	A2#	43.687	4.17	43.687	4.17	0.00	100.0	PASS 合格
	A3#	43.735	4.17	43.735	4.17	0.00	100.0	PASS 合格
	A4#	43.454	4.17	43.454	4.17	0.00	100.0	PASS 合格
Fully charged at first cycle	A5#	43.862	4.17	43.862	4.17	0.00	100.0	PASS 合格
首次循环满电状态	A6#	43.097	4.17	43.097	4.17	0.00	100.0	PASS 合格
	A7#	43.517	4.17	43.517	4.17	0.00	100.0	PASS 合格
A	A8#	43.687	4.17	43.687	4.17	0.00	100.0	PASS 合格
	A9#	43.744	4.17	43.744	4.17	0.00	100.0	PASS 合格
	A10#	43.636	4.17	43.548	4.17	0.00	100.0	PASS 合格

Notes 注释:

After the test, there is no leakage, no venting, no disassembly, no rupture and no fire.

http://www.ntek.org.cn



测试后,电芯未渗漏、未泄气、未解体、未破裂和未起火。 Room temperature 环境温度: 20.3°C

Test T.2: Thermal test 试验T.2: 温度试验

Test method 测试方法

Cells are to be stored for at least six hours at a test temperature equal to 72 ± 2°C, followed by storage for at least six hours at a test temperature equal to -40 ± 2°C. The maximum time interval between test temperature extremes is 30 minutes. This procedure is to be repeated 10 times, after which all test cells are to be stored for 24 hours at ambient temperature (20 ± 5°C).

电芯放置在试验温度等于72±2°C的条件下存放至少6小时,接着再在试验温度等于-40±2°C的条件下存放至少6 小时。两个极端试验温度之间的最大时间间隔为30分钟。此程序重复进行,共完成10次,接着将所有试验电芯在 环境温度(20±5°C)下存放24小时。

Requirement 要求

Cells meet this requirement if there is no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell after testing is not less than 90% of its voltage immediately prior to this procedure.

电芯须无渗漏、无泄气、无解体、无破裂和无起火,并且每个试验电芯在试验后的开路电压不小于其在进行这一 试验前电压的90%。

Test Data showed in table below 测试数据见下表

		Prior to te	est 试验前	After tes	t 试验后		Voltage after	
State of samples 样品状态	No. 编号	Mass 质量 (g)	Voltage 电压 (V)	Mass 质量 (g)	Voltage 电压 (V)	Mass loss 质量损 失 (%)	test/ voltage prior to test (%) 试验后电压/试验前电压	Results 结果
	A1#	43.548	4.17	43.526	4.14	0.051	99.28	PASS 合格
	A2#	43.687	4.17	43.659	4.14	0.064	99.28	PASS 合格
	A3#	43.735	4.17	43.720	4.13	0.034	99.04	PASS 合格
Fully charged at first cycle	A4#	43.454	4.17	43.432	4.14	0.051	99.28	PASS 合格
首次循环满电状 态	A5#	43.862	4.17	43.843	4.13	0.043	99.04	PASS 合格
	A6#	43.097	4.17	43.069	4.14	0.065	99.28	PASS 合格
	A7#	43.517	4.17	43.503	4.14	0.032	99.28	PASS 合格
	A8#	43.687	4.17	43.668	4.14	0.044	99.28	PASS 合格



A9#	43.744	4.17	43.725	4.13	0.043	99.04	PASS 合格
A10#	43.636	4.17	43.618	4.14	0.041	99.28	PASS 合格

Notes 注释:

After the test, there is no leakage, no venting, no disassembly, no rupture and no fire.

测试后,电芯未渗漏、未泄气、未解体、未破裂和未起火。

Room temperature 环境温度: 21.5°C

Test T.3: Vibration 试验T.3: 振动

Test method 测试方法

Cells are firmly secured to the platform of the vibration machine without distorting the cells in such a manner as to faithfully transmit the vibration. The vibration is a sinusoidal waveform with a logarithmic sweep between 7 Hz and 200 Hz and back to 7 Hz traversed in 15 minutes. This cycle is repeated 12 times for a total of 3 hours for each of three mutually perpendicular mounting positions of the cell. One of the directions of vibration must be perpendicular to the terminal face.

The logarithmic frequency sweep is as follows: from 7 Hz a peak acceleration of 1 g_n is maintained until 18 Hz is reached. The amplitude is then maintained at 0.8 mm (1.6 mm total excursion) and the frequency increased until a peak acceleration of 8 g_n occurs (approximately 50 Hz). A peak acceleration of 8 g_n is then maintained until the frequency is increased to 200 Hz.

电芯紧固于振动台台面,但不得造成电芯变形,并能准确可靠地传播振动。振动应是正弦波形,对数扫描频率在 7 Hz和200 Hz之间,再回到7 Hz,1次循环时间为15分钟。这一振动过程须对三个互相垂直的电池安装方位的每一方向重复进行12次,总共为时3小时。其中一个振动方向必须与端面垂直。

对数扫频方式: 从7 Hz开始,保持1 g_n 的最大加速度,直到频率达到18 Hz。然后将振幅保持在0.8mm(总位移 1.6mm),并增加频率直到峰值加速度达到8 g_n (频率约为50 Hz)。将峰值加速度保持在8 g_n 直到频率增加到200 Hz。

Requirement 要求

Cells meet this requirement if there is no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell after testing is not less than 90% of its voltage immediately prior to this procedure.

电芯须无渗漏、无泄气、无解体、无破裂和无起火,并且每个试验电芯在试验后的开路电压不小于其在进行这一试验前电压的**90%**。

Test Data showed in table below 测试数据见下表

	Prior to test 试验前		After test 试验后			Voltage after		
State of	No.	Mass	Voltage	Mass	Voltage	Mass loss	test/ voltage prior to test	Results
samples	编号	质量	电压	质量	电压	质量损	(%)	结果
样品状态		(g)	(V)	(g)	(V)	失 (%)	试验后电压/	
							试验前电压	
Fully charged	A1#	43.526	4.14	43.526	4.14	0.00	100.0	PASS

Shenzhen NTEK Testing Technology Co., Ltd.

Tel: +86-755-6115 6588

Fax: +86-755-6115 6599

http://www.ntek.org.cn

Page 9 of 14 第 9 页 共 14 页





at first cycle								合格
首次循环满电状	A2#	43.659	4.14	43.659	4.14	0.00	100.0	PASS
态	AZ#	43.039	4.14	43.039	4.14	0.00	100.0	合格
	A3#	43.720	4.13	43.720	4.13	0.00	100.0	PASS
	7.0#	45.720	4.10	40.720	7.10	0.00	100.0	合格
	A4#	43.432	4.14	43.432	4.14	0.00	100.0	PASS
	//4#	45.452	7.17	75.752	7.17	0.00	100.0	合格
	A5#	43.843	4.13	43.843	4.13	0.00	100.0	PASS
	Λ3#	45.045	7.10	45.045	4.10	0.00	100.0	合格
	A6#	43.069	4.14	43.069	4.14	0.00	100.0	PASS
	Α0#	45.009	4.14	45.009	7.17	0.00	100.0	合格
	A7#	43.503	4.14	43.503	4.14	0.00	100.0	PASS
	\(\frac{1}{4}\)	43.303	7.17	45.505	7.17	0.00	100.0	合格
	A8#	43.668	4.14	43.668	4.14	0.00	100.0	PASS
	A0#	45.000	4.14	43.000	4.14	0.00	100.0	合格
C-1000	A9#	43.725	4.13	43.725	4.13	0.00	100.0	PASS
	A3#	43.725	4.13	45.725	4.13	0.00	100.0	合格
	A10#	43.618	4.14	43.618	4.14	0.00	100.0	PASS
	A10#	43.010	4.14	43.010	4.14	0.00	100.0	合格

Notes 注释:

After the test, there is no leakage, no venting, no disassembly, no rupture and no fire.

测试后, 电芯未渗漏、未泄气、未解体、未破裂和未起火。

Room temperature 环境温度: 20.3°C

Test T.4: Shock 试验 T.4: 冲击

Test method 测试方法

Cells are secured to the testing machine by means of a rigid mount which will support all mounting surfaces of each test cell. Each cell is subjected to a half-sine shock of peak acceleration of 150 g_n and pulse duration of 6 milliseconds. Each cell is subjected to three shocks in the positive direction followed by three shocks in the negative direction of three mutually perpendicular mounting positions of the cell for a total of 18 shocks. 试验电芯用刚性支架紧固在试验装置上,支架支撑着每个试验电芯的所有安装面。每个电芯须经受峰值加速度150 gn和脉冲持续时间6 ms的半正弦波冲击。每个电芯须在三个互相垂直的电芯安装方位的正方向经受三次冲击,接着在反方向经受三次冲击,总共经受18次冲击。

Requirement 要求

Cells meet this requirement if there is no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell after testing is not less than 90% of its voltage immediately prior to this procedure.

电芯须无渗漏、无泄气、无解体、无破裂和无起火,并且每个试验电芯在试验后的开路电压不小于其在进行这一试验前电压的**90%**。

Test Data showed in table below 测试数据见下表

Shenzhen NTEK Testing Technology Co., Ltd.
Tel: +86-755-6115 6588 Fax: +86-755-6115 6599
http://www.ntek.org.cn





		Prior to te	est 试验前	After tes	t 试验后		Voltage after	
State of samples 样品状态	No. 编号	Mass 质量 (g)	Voltage 电压 (V)	Mass 质量 (g)	Voltage 电压 (V)	Mass loss 质量损 失 (%)	test/ voltage prior to test (%) 试验后电压/试验前电压	Results 结果
	A1#	43.526	4.14	43.526	4.14	0.00	100.0	PASS 合格
	A2#	43.659	4.14	43.659	4.14	0.00	100.0	PASS 合格
	A3#	43.720	4.13	43.720	4.13	0.00	100.0	PASS 合格
	A4#	43.432	4.14	43.432	4.14	0.00	100.0	PASS 合格
Fully charged at first cycle	A5#	43.843	4.13	43.843	4.13	0.00	100.0	PASS 合格
首次循环满电状 态	A6#	43.069	4.14	43.069	4.14	0.00	100.0	PASS 合格
	A7#	43.503	4.14	43.503	4.14	0.00	100.0	PASS 合格
	A8#	43.668	4.14	43.668	4.14	0.00	100.0	PASS 合格
	A9#	43.725	4.13	43.725	4.13	0.00	100.0	PASS 合格
	A10#	43.618	4.14	43.618	4.14	0.00	100.0	PASS 合格

Notes 注释:

After the test, there is no leakage, no venting, no disassembly, no rupture and no fire.

测试后,电芯未渗漏、未泄气、未解体、未破裂和未起火。

Room temperature 环境温度: 21.2°C

Test T.5: External short circuit 试验T.5: 外部短路

Test method 测试方法

Cells to be tested are heated for a period of time necessary to reach a homogeneous stabilized temperature of 57 ± 4 °C, measured on the external case. This period of time depends on the size and design of the cell and is assessed and documented. Then the battery at 57 ± 4 °C is subjected to one short circuit condition with a total external resistance of less than 0.1 ohm.

This short circuit condition is continued for at least one hour after the cell external case temperature has returned to 57 ± 4 °C.

The short circuit and cooling down phases are conducted at least at ambient temperature.

试验电芯首先被加热或恒定一段时间,使其达到57±4°C并使其外表面温度均匀恒定在57±4°C。该加热时间

Shenzhen NTEK Testing Technology Co., Ltd.
Tel: +86-755-6115 6588 Fax: +86-755-6115 6599
http://www.ntek.org.cn



或热恒定时间的长短取决于该电芯的尺寸和设计,并同时加以评估及提供文件证明。然后该电芯在 57 ± 4 °C的条件下承受一个外部总阻抗小于0.1Ω的短路条件。

该短路测试持续到电芯外表面温度返回至57±4°C后再保持至少1小时。

该短路和冷却阶段均被执行在57±4°C的环境温度下。

Requirement 要求

Cells meet this requirement if their external temperature does not exceed 170°C and there is no disassembly, no rupture and no fire during the test and within six hours after the test.

电芯外壳温度不超过170°C,并且在试验过程中及试验后6小时内无解体、无破裂,无起火。

Test data showed in table below 测试数据见下表

State of samples	No.	Maximum outer casing temperature	Results
样品状态	编号	电池表面最高温度 (°C)	结果
	A1#	67.1	PASS 合格
	A2#	63.8	PASS 合格
	A3#	59.6	PASS 合格
	A4#	70.3	PASS 合格
Fully charged at first cycle	A5#	65.7	PASS 合格
首次循环满电状态	A6#	65.1	PASS 合格
	A7#	57.4	PASS 合格
	A8#	66.4	PASS 合格
	A9#	65.5	PASS 合格
	A10#	70.1	PASS 合格

Notes 注释:

There is no disassembly, no rupture and no fire during the test and within six hours after test.

电芯在测试中和测试后6小时内未解体、未破裂,未起火。

Room temperature 环境温度: 19.4°C

Test T.6: Impact 试验T.6: 撞击

Test method 测试方法

Each cell is to be placed on a flat smooth surface. A 15.8 mm ± 0.1 mm diameter, at least 6 cm long, or the longest dimension of the cell, whichever is greater, Type 316 stainless steel bar is to be placed across the centre of the sample. A 9.1 kg \pm 0.1 kg mass is to be dropped from a height of 61 \pm 2.5 cm at the intersection of the bar and sample in a controlled manner using a near frictionless, vertical sliding track or channel with minimal drag on the falling mass. The vertical track or channel used to guide the falling mass is oriented 90 degrees from the horizontal supporting surface.

The test sample is to be impacted with its longitudinal axis parallel to the flat surface and perpendicular to the longitudinal axis of the 15.8 mm \pm 0.1mm diameter curved surface lying across the centre of the test sample. Each sample is to be subjected to only a single impact.

每个电芯放在平坦光滑的表面上。一根 316 型不锈钢棒横放在试样中心,钢棒直径 15.8±0.1 毫米,长度至少 6 厘米,或电芯的最长尺度,取二者中较大者。将一块 9.1±0.1 kg 的重锤从 61±2.5 厘米高处跌落到钢棒和试样



交叉点,使用一个几乎没有摩擦的、对落体重锤阻力很小的垂直导轨或管道加以控制。垂直导轨或管道用于引导 落锤沿与水平支撑表面呈 90 度落下。

接受撞击的试样,纵轴应与测试平面平行并与横放在试样中心的直径 15.8±0.1 毫米弯曲表面的纵轴垂直。每一试样只经受一次撞击。

Requirement 要求

Cells meet this requirement if their external temperature does not exceed 170°C and there is no disassembly and no fire during the test and within six hours after the test.

元件电池芯外壳温度不超过170°C,并且在试验过程中及试验后6小时内无解体,无起火。

Test data showed in table below 测试数据见下表

State of samples 样品状态	No. 编号	Maximum outer casing temperature 电池表面最高温度 (°C)	Results 结果
50% charged of the	A11#	123.0	PASS 合格
design rated capacity	A12#	105.1	PASS 合格
at first cycle	A13#	120.8	PASS 合格
首次循环 50%充电状	A14#	130.7	PASS 合格
态	A15#	127.6	PASS 合格

Notes 注释:

There is no disassembly, no rupture and no fire during the test and within six hours after test.

电芯在测试中和测试后 6 小时内未解体、未起火。

Room temperature 环境温度: 22.1°C

Test T.8: Forced discharge 试验 T.8: 强制放电

Test method 测试方法

Each cell is forced discharged at ambient temperature by connecting it in series with a 12V D.C. power supply at an initial current equal to the maximum discharge current specified by the manufacturer.

The specified discharge current is to be obtained by connecting a resistive load of the appropriate size and rating in series with the test cell. Each cell is forced discharged for a time interval (in hours) equal to its rated capacity divided by the initial test current (in ampere).

每个电芯在环境温度下与 12V 直流电电源串联在起始电流等于制造商给定的最大放电电流的条件下强制放电。 电芯与一个适当大小的电阻负载串联以调节到规定大小的放电电流。每块电芯的放电时间(单位为 h)等于电芯的额定容量除以试验初始放电电流(单位 A)。


Requirement 要求

Cells meet this requirement if there is no disassembly and no fire during the test and within seven days after the test.

电芯在试验过程中和试验后7天内无解体,无起火。

Test data showed in table below 测试数据见下表

Initial current 初始电流(mA)	4400mA
Supply voltage 试验电压(Vdc)	12Vdc





State of samples	No.	Results
样品状态	编号	结果
Fully discharged at first cycle 首次循环完全放电状态	A16#	PASS 合格
	A17#	PASS 合格
	A18#	PASS 合格
	A19#	PASS 合格
	A20#	PASS 合格
	A21#	PASS 合格
	A22#	PASS 合格
	A23#	PASS 合格
	A24#	PASS 合格
	A25#	PASS 合格
Fully discharged after fifty cycles 50 个循环后完全放电状态	A26#	PASS 合格
	A27#	PASS 合格
	A28#	PASS 合格
	A29#	PASS 合格
	A30#	PASS 合格
	A31#	PASS 合格
	A32#	PASS 合格
	A33#	PASS 合格
	A34#	PASS 合格
	A35#	PASS 合格

Notes 注释:

There is no disassembly and no fire during the test and within seven days after the test. 电芯在测试中和测试后 7 天内未解体,未着火。

Room temperature 环境温度: 19.5°C

*******End of Test Report 检测报告结束*******

Important

注意事项

- 1. The test report is invalid without the Report Seal of NTEK and Paging seal of NTEK. 本报告书无本公司报告专用章、骑缝章无效.
- 2. Nobody is allowed to photocopy or partly photocopy this test report without written permission of NTEK.

未经本公司书面同意,不得部分地复制本报告书。

3. The test report is invalid without the signatures of Ratifier, Reviewer and Testing engineer.

本报告书无批准人、审核人、及主检人签名无效。

- 4. The report is invalid when anything of following happens illegal transfer, reproduce, embezzlement, imposture, modification or tampering in any media form. 私自转让、复制、盗用、冒用、涂改、或以任何媒体形式篡改的报告书无效。
- 5. Objections to the test report must be submitted to NTEK within 15 days. 对报告书若有异议,应于收到报告之日起15天内向本公司提出。
- 6. The test report is valid for the tested samples only. 本报告仅对测试样品有效。
- 7. The Chinese contents in this report are only for reference. 本报告中的中文内容仅供参考。

深圳市北测检测技术有限公司

Shenzhen NTEK Testing Technology Co., Ltd.

地址:深圳市宝安区西乡三围奋达科技园 E 栋 1 楼

Address: 1/F, Building E, Fenda Science Park, Sanwei Community, Xixiang Street, Bao'an District, Shenzhen

518126 P.R. China

Tel: +86-755-6115 6588 Fax: +86-755-6115 6599

Email: coco@ntek.org.cn Kevin@ntek.org.cn

http://www.ntek.org.cn